


## Acoustical Absorption Coefficient according to ISO 354

Object: TOPAKUSTIK® wall- and ceiling panelling  
Type TOPAKUSTIK® 9/2 M 6%




Research: Laboratory: SWISSCOM AG 03.05.1999  
Test area: 12 m<sup>2</sup> Relative atmospheric humidity: 55%  
Echo space volume: 214.3 m<sup>3</sup> Temperature: 20 degrees

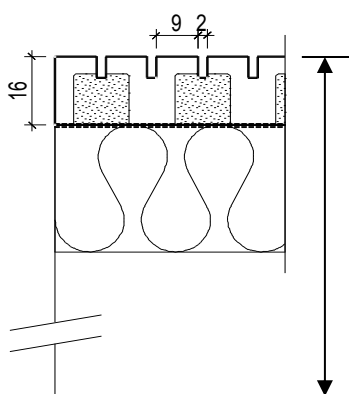

TOPAKUSTIK® 9/2 M  
Acoustic fleece

Mineral wool 30 mm


**Suspension heights:**  
**216/76 mm**  
Cavity 170/30 mm

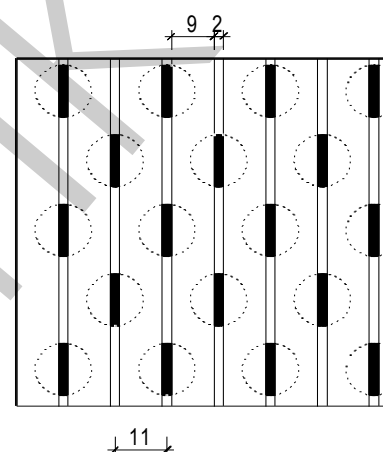

## Acoustical Absorption - Medium values

Low frequency range: (100-315 Hz): 0.58  
Medium frequency range: (400-1250 Hz): 0.88  
High frequency range: (1600-5000 Hz): 0.66

Freq.	
[Hz]	Terz
100	0.27
125	0.33
160	0.46
200	0.75
250	0.77
315	0.90
400	0.93
500	0.90
630	0.85
800	0.85
1000	0.88
1250	0.86
1600	0.82
2000	0.74
2500	0.64
3150	0.60
4000	0.59
5000	0.57

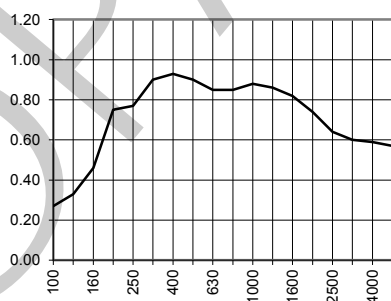
**Suspension height 216 mm**

**EN**  **$\alpha_w$**  **NRC**  
**C** **0.75 (L)** **0.82**

## Acoustical Absorption - Medium values

Low frequency range: (100-315 Hz): 0.42  
Medium frequency range: (400-1250 Hz): 0.98  
High frequency range: (1600-5000 Hz): 0.64

Freq.	
[Hz]	Terz
100	0.09
125	0.13
160	0.27
200	0.43
250	0.72
315	0.89
400	1.01
500	1.08
630	1.04
800	1.00
1000	0.94
1250	0.80
1600	0.74
2000	0.71
2500	0.66
3150	0.63
4000	0.56
5000	0.54

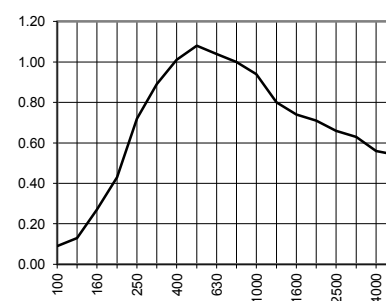**Suspension height 76 mm**

**EN**  **$\alpha_w$**  **NRC**  
**C** **0.75 (M)** **0.86**